# **Tension Model**

The computation of flexural strength  $M_n$  based on the approximate parabolic stress distribution shown in Figure 1 may be done using the given  $k_2/(k_1k_3)$  values. However, it is desirable to have a simple method that uses fundamental static equilibrium.

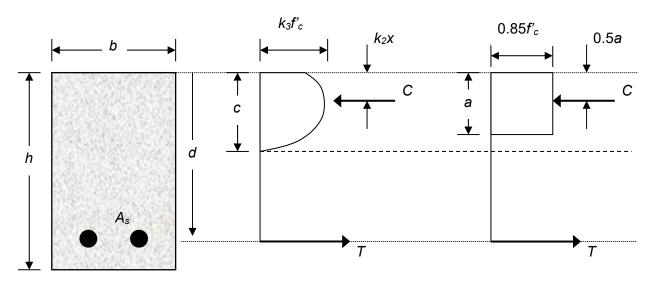


Figure 1. Definition of Whitney Rectangular Stress Distribution

In the 1930s, Whitney (1937) proposed using a rectangular compressive stress distribution to replace the parabolic stress distribution. As shown in Figure 1, an average stress of  $0.85f_c$  is used with a rectangle of depth  $a = \beta_1 c$ . Whitney determined that  $\beta_1$  should be 0.85 for concrete with  $f_c > 4,000$  psi and 0.05 less for each 1,000 psi of  $f_c$  above 4,000 psi. The value of  $\beta_1$  may not be taken to less than 0.65 (ACI 2011). The concrete below the neutral axis is ignored, and the total tension force T is due to the reinforcing steel. The Whitney stress block is used to estimate the compression force C.

The bending strength  $M_0$  using the equivalent rectangle is obtained from Figure 1 as follows

$$C = 0.85f_c'ba \tag{1}$$

$$T = A_{\rm s} f_{\rm y} \tag{2}$$

where  $f_y$  is the yield stress of the steel reinforcement (assuming that the steel yields before crushing the concrete). Equating C = T gives:

$$a = \frac{A_s f_y}{0.85 f_c' b} \tag{3}$$

The bending strength is computed as the tensile force multiplied by the distance between the forces.

$$M_n = A_s f_y \left( d - \frac{a}{2} \right) \tag{4}$$

Combining the above Equations (3) and (4) gives:

$$M_n = A_s f_y \left( d - 0.59 \frac{A_s f_y}{f_c' b} \right) \tag{5}$$

The ACI Code explicitly accepts the Whitney rectangle (ACI 2011). For the loading conditions in this reinforced concrete beam competition, the ultimate force due to tensile would be:

$$P_{tension} = \frac{A_s f_y}{4} \left( d - 0.59 \frac{A_s f_y}{f_c' b} \right)$$
 (6)

#### **Shear Model**

The design of shear reinforcement is based on the assumption that the shear force must not exceed the total shear capacity of the beam (ACI 2011). When shear reinforcement is used, the shear capacity of a beam cross-section can be estimated as

$$V_n = V_s + V_c \tag{7}$$

where  $V_n$  is the shear force in the beam,  $V_s$  is the shear capacity supplied by the reinforcement, and  $V_c$  is the shear strength of the concrete. The shear capacity of the reinforcement, which is assumed to be uniformly spaced across the diagonal crack, is

$$V_n = \frac{A_v f_y d}{s} + 2\sqrt{f'_c} bd \tag{8}$$

where  $A_{\nu}$  is the area of steel reinforcement in shear for each stirrup crossing the diagonal crack, and s is the spacing of the stirrups. For the loading conditions in this reinforced concrete beam competition, the ultimate force due to shear would be:

$$P_{shear} = 2\left(\frac{A_{v}f_{y}d}{s} + 2\sqrt{f'_{c}}bd\right)$$
 (9)

# **Compression Model**

The reinforcement ratio  $\rho$  (often called reinforcement percentage) may conveniently represent a beam's relative amount of tension reinforcement. Thus, using the dimensions of Figure 1, the reinforcement ratio is:

$$\rho = \frac{A_s}{bd} \tag{10}$$

Rewriting Equation (10) expresses the reinforcement ratio in terms of the *c/d* ratio.

$$\rho = 0.85 \beta_1 \frac{c}{d} \frac{f_c'}{f_v'} \tag{11}$$

For beams controlled by tensile failure, c/d < 0.375 (ACI 2011).

If the c/d > 0.6, beam failure is controlled by compression (ACI 2011). For an overly reinforced beam, the stress in the tensile steel  $f_{steel}$  when the concrete reaches its ultimate strain is:

$$f_{\text{steel}} = 87,000 \, psi \left( \frac{d-c}{c} \right) \tag{12}$$

If  $f_{steel} < f_y$  or c/d > 0.6, then the maximum moment in compression is:

$$M_{compression} = A_{s} \left( \frac{d-c}{c} \right) \left( d - \frac{a}{2} \right) 87,000 \, psi$$
 (13)

For the loading conditions in this reinforced concrete beam competition, the ultimate force due to compression would be:

$$P_{compression} = \frac{A_{s}}{4} \left( \frac{d-c}{c} \right) \left( d - \frac{a}{2} \right) 87,000 \, psi$$
 (14)

# **Estimation of Beam Weight and Cost**

The estimated weight W of a simply reinforced rectangular concrete beam is

$$W = V_{beam} \gamma_{concrete} + A_s L (\gamma_{steel} - \gamma_{concrete})$$
 (15)

where  $V_{beam}$  is the volume of the beam, L is the length of the beam,  $\gamma_{concrete}$  is the unit weight of concrete (typically 145 lb./ft.<sup>3</sup>), and  $\gamma_{steel}$  is the unit weight of steel (490 lb./ft.<sup>3</sup>).

The total cost estimate for a reinforced concrete beam  $C_{beam}$  is

$$C_{beam} = C_{steel} + C_{concrete}$$
 (16)

where  $C_{steel}$  is the cost of the steel reinforcement, and  $C_{concrete}$  is the cost of the concrete. Table 1 lists the unit cost for a reinforced concrete beam for this competition.

Material	Cost
Portland Type I cement	\$150/ton
Coarse aggregate	\$18/ton
Fine aggregate	\$10/ton
Steel reinforcement	\$700/ton
Admixtures - water reducer	\$15/gal
Admixture - silica flume	\$500/top

Table 1. Reinforced Concrete Material Cost

To compute the cost of a reinforced concrete beam using the information in Table 1, use the following estimates (there is no cost associated with shear reinforcement).

The cost of the steel,  $C_{steel}$ , may be estimated as follows:

$$C_{\text{steel}} = A_{\text{s}} L \left(490 \frac{\text{lb.}}{\text{ft.}^3}\right) \left(\frac{\$700}{\text{ton}}\right) \left(\frac{\text{ton}}{2,000 \text{ lb.}}\right)$$
(17)

The total cost of concrete, Cconcrete, is estimated from the mix design as

$$C_{concrete} = C_{cement} + C_{CA} + C_{FA} \tag{18}$$

where  $C_{cement}$  is the cost of the cement,  $C_{CA}$  is the cost of the coarse aggregate, and  $C_{FA}$  is the cost of the fine aggregate. The cost of each of these components can be computed as

$$C_{cement} = V_{beam} \left( W_{cement} \frac{\text{lb.}}{\text{ft.}^3} \right) \left( \frac{\$150}{\text{ton}} \right) \left( \frac{150}{2,000 \text{ lb.}} \right)$$
 (19)

$$C_{CA} = V_{beam} \left( W_{CA} \frac{\text{lb.}}{\text{ft.}^3} \right) \left( \frac{\$18}{\text{ton}} \right) \left( \frac{\text{ton}}{2,000 \text{ lb.}} \right)$$
 (20)

$$C_{FA} = V_{beam} \left( W_{FA} \frac{\text{lb.}}{\text{ft.}^3} \right) \left( \frac{\$10}{\text{ton}} \right) \left( \frac{\text{ton}}{2,000 \text{ lb.}} \right)$$
 (21)

where  $W_{cement}$  is the weight of cement,  $W_{CA}$  is the weight of coarse aggregate, and  $W_{FA}$  is the weight of fine aggregate (each weight is per ft.<sup>3</sup> of concrete).

### **Estimation of Cost-Adjusted SWR**

The ultimate strength S of the reinforced concrete beam may be estimated based on the value of c/d as follows (ACI 2011):

If 
$$\frac{c}{d} \le 0.375$$
  $S = Minimun(P_{tension}, P_{shear})$ 

$$0.375 < \frac{c}{d} < 0.6 \quad S = Minimun(P_{tension}, P_{shear}, P_{compression})$$

$$\frac{c}{d} \ge 0.6 \quad S = Minimun(P_{compression}, P_{shear})$$
(22)

The predicted strength-to-weight ratio SWR is

$$SWR = \frac{S}{W}$$
 (23)

The predicted value of the cost-adjusted ASWR may be computed as follows:

If 
$$C_{Beam} < \$2$$
  $ASWR = SWR$   
 $> \$2$   $ASWR = SWR \left(\frac{\$2}{C_{Beam}}\right)$  (24)

#### References

American Concrete Institute (2011). Building Code Requirements for Structural Concrete (ACI 318-11) and Commentary.

Whitney, C.S. (1937) "Design of Reinforced Concrete Members Under Flexure and Combined Flexure and Direct Compression." *ACI Journal*, March-April; 33, 483-498.